

## Standard Test Method for Bulk Density of Level Paintbrush Filaments<sup>1</sup>

This standard is issued under the fixed designation D 5959; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers a procedure for measuring the weight of filaments per unit volume.

1.2 This test method is applicable only to monofilament with consistent longitudinal (level) profiles.

1.3 The values given in inch-pound units are to be regarded as the standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Summary of Test Method

2.1 The weight and volume of a bundle of filaments is measured, and the bundle density is calculated.

### 3. Significance and Use

3.1 Filaments are available in a variety of cross sections and materials. A measure of bulk density permits the brushmaker to estimate the weight of filament required to prepare a given number of brushes.

### 4. Apparatus

4.1 The apparatus requires some machining, and is assembled as shown in Fig. 1 from the following equipment:

4.1.1 Air Valve<sup>2</sup>

4.1.2 Miniature Air Cylinder,<sup>3</sup> dual acting, heavy duty.

4.1.3 Assorted parts shown in Fig. 1 are machined from 304 stainless steel and assembled as shown along with the air valve and cylinder just described. The scale must be fixed in place so

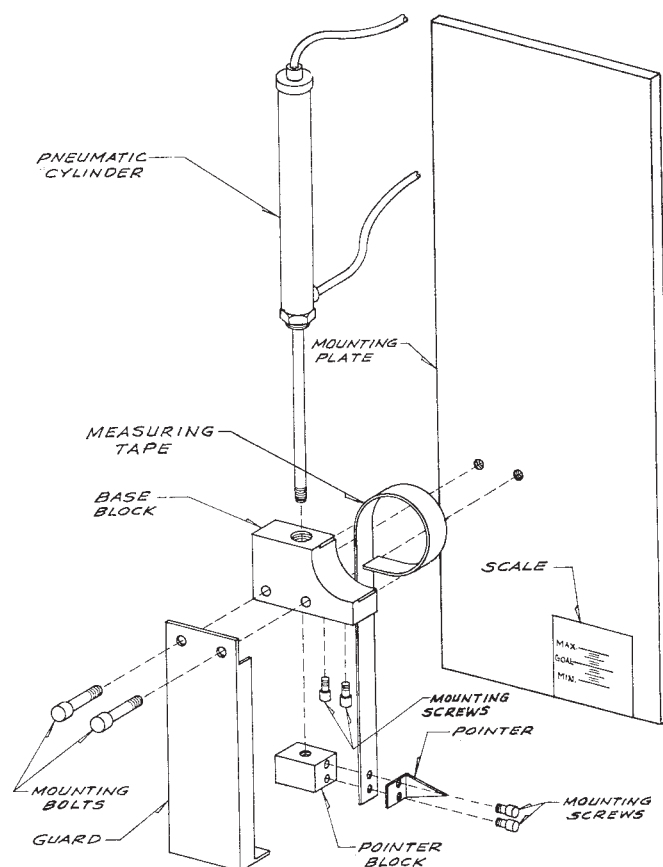


FIG. 1 Apparatus to Measure Bundle Diameter

that it reads accurately the diameters of metal standards that are 1.82 in. (46.2 mm) and 2.06 in. (52.3 mm) diameter.<sup>4</sup>

4.2 *Weighing Device*, accurate to 0.1 g to weigh the bundle.

4.3 *Scale*, accurate to 0.02 in. (0.5 mm) to measure the bundle length.

4.4 *Air Supply*, with pressure regulator set for 50 psig.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.61 on Paint Application Tools.

Current edition approved July 10, 2003. Published July 2003. Originally approved in 1996. Last previous addition approved in 1996 as D 5959 - 96.

<sup>2</sup> Air valve such as Model 6676 available from Hunt Valve Co., 1913 E. State Street, Salem, Ohio 44460, or equivalent, has been found suitable for this purpose.

<sup>3</sup> Miniature air cylinder such as Model H95-5D, 1/16-in. (14.3-mm) bore, 5-in. (127-mm) stroke, dual acting, heavy duty, available from Clippard Instrument Laboratory, 7390 Colerain Road, Cincinnati, OH 45239, or equivalent, has been found suitable for this purpose.

<sup>4</sup> An assembled bulk density test device available from T. S. Simms and Co., 33 Bridge Road, St. John, New Brunswick, Canada E21 E2L 4C5, or equivalent, has been found suitable for this purpose.

4.5 *Calibration Standards*, 1.82 (46.2 mm) and 2.06 in. (52.3 mm) in diameter.<sup>5</sup>

## 5. Sampling, Test Specimens and Test Units

5.1 The test result will depend on the cross-sectional shape, the polymer, and the length of the bundle selected for the test. To a lesser extent it will also depend on the filament diameter since thin filaments pack more efficiently than large ones.

5.2 The device, as pictured in Fig. 1, is designed to measure diameters ranging from 1.82 to 2.06 in. (46.2 to 52.3 mm). Make sure that both ends are measured and the results are averaged.

## 6. Procedure

6.1 Select a sample of approximately 2-in. (50-mm) diameter. Filament may be removed from a sample so the bundle diameter falls within the scale range (1.82 to 2.06 in.) (46.2 to 52.3 mm). One convenient method to adjust the sample diameter to the desired range is to fill a 2-in. (50-mm) inside diameter tube. If the sample is too small, like samples may be combined to adjust the bundle diameter to the desired range.

6.2 Weigh the sample bundle to the nearest 0.1 g ( $W$ ). Make sure that the weight excludes the wrap or rubber bands used to hold the filament together.

6.3 Measure the lengths of five individual filaments to the nearest 0.02 in. (0.5 mm) with a ruler and average the lengths to determine bundle length ( $L$ ).

6.4 With rubber bands holding the bundle together, roll it between the palms of the hands four times and then place the

end of the bundle inside the loop of measuring tape in the device shown in Fig. 1. Operate the air valve lever 10 times to stabilize. Actuate the air valve to tighten the steel tape. Read the bundle diameter, estimating to the nearest 0.005 in. (0.1 mm) from where the pointer indicates on the scale.

6.5 Release the bundle. Reverse the bundle end for end and repeat 6.4 to remeasure the diameter.

6.6 Average the results ( $D$ ) and proceed to calculate the bulk density as described in 7.1. Bulk density is expressed in  $\text{g/in.}^3$  ( $\text{g/cm}^3$ ).

## 7. Calculation or Interpretation of Results

7.1 Calculate bulk density as follows:

$$\text{Bulk Density} = 4 \times W / (L \times \pi \times D^2) \quad (1)$$

where:

$W$  = bundle weight, g,

$L$  = bundle length, in. (cm), and

$D$  = mean bundle diameter, in. (cm).

## 8. Precision and Bias

8.1 *Precision*—Measurements of bulk density of solid, level filament at five laboratories agreed within  $\pm 0.2 \text{ g/in.}^3$  or  $\pm 1 \%$ . Repeatability within the laboratory for four bundles was  $\pm 0.1 \text{ g/in.}^3$  for solid and  $\pm 0.2 \text{ g/in.}^3$  for hollow.

8.2 *Bias*—Since there is no accepted reference material suitable for determining the bias for the procedure in this test method, no statement on bias can be made.

## 9. Keywords

9.1 bulk density; density; filaments; paint brush

<sup>5</sup> Steel cylinders machined to diameters of 1.82 in. with a tolerance of 0.001 in. (46.2 mm with a tolerance of 0.02 mm) and 2.06 in. with a tolerance of 0.001 in. (52.3 mm with a tolerance of 0.02 mm).

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*